



## Technical Information: S7


**S7 IS AN AIR HARDENING, SHOCK RESISTANT, COLD WORK TOOL STEEL**  
**S7 IS CHARACTERIZED BY HIGH IMPACT TOUGHNESS AT RELATIVELY HIGH HARDNESS LEVELS**  
**S7 IS ALSO USED FOR PLASTIC MOLD TOOLING REQUIRING HIGH TOUGHNESS LEVELS**

**TYPICAL CHEMICAL COMPOSITION**

<b>CARBON</b>	<b>0.55%</b>	<b>CHROMIUM</b>	<b>3.25%</b>
<b>MOLYBDENUM</b>	<b>1.40%</b>	<b>SILICON</b>	<b>0.35%</b>
<b>VANADIUM</b>	<b>0.25%</b>	<b>MANGANESE</b>	<b>0.70%</b>

### TOOL STEEL PROPERTIES COMPARISON

■ Relative Wear Resistance    ■ Chipping Resistance

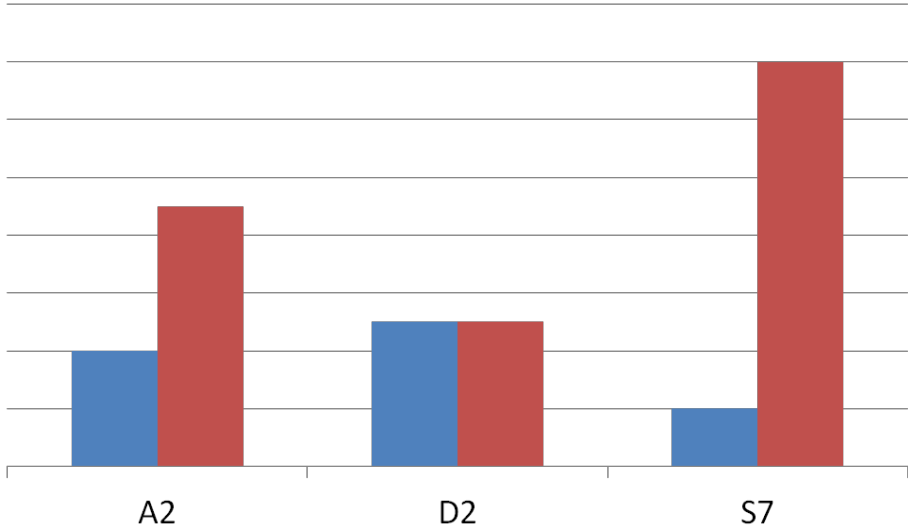

### PHYSICAL PROPERTIES

- MODULUS OF ELASTICITY**.....30 PSI X 10<sup>6</sup> .....(207 GPA)
- DENSITY**..... 0.283 LB/IN<sup>3</sup>
- ANNEALED HARDNESS**.....210-225 BRINELL HARDNESS (BHN)
- MACHINABILITY**.....SIMILAR TO A2 TOOL STEEL

## Technical Information: S7

### HEAT TREATMENT

#### ANNEALING

HEAT TO 1550°F, HOLD TWO HOURS  
SLOW COOL 20°F/HOUR TO 900°F  
THEN AIR OR FURNACE COOL TO ROOM TEMPERATURE

#### STRESS RELIEVING

PERFORMED PRIOR OR AFTER MACHINING TO MINIMIZE DISTORTION IN HEAT TREATING  
1100/1200°F, HOLD TWO HOURS  
THEN AIR COOL TO ROOM TEMPERATURE

#### HARDENING

SALT BATH, PROTECTIVE ATMOSPHERE, OR VACUUM FURNACE EQUIPMENT PREFERRED.

#### HIGH HEAT (AUSTENITIZING)

1750°F FOR 30 MINUTES AT HEAT.

#### QUENCH

SALT BATH QUENCH TO 1000-1100°F, EQUALIZE, THEN AIR COOL TO 150°F .  
VACUUM OR ATMOSPHERE QUENCH RATE OF A MINIMUM 50 DEGREES F PER MINUTE DOWN TO 900°F IS  
CRITICAL TO ACHIEVE BEST HEAT TREAT RESPONSE.

TEMPER IMMEDIATELY FOLLOWING QUENCH WHEN MATERIAL REACHES 150°F OR BELOW.

#### TEMPERING

MINIMUM 400°F TEMPERING TEMPERATURE REQUIRED.  
DOUBLE TEMPERING IS REQUIRED, TRIPLE TEMPERING RECOMMENDED.  
AIR COOL TO ROOM TEMPERATURE BETWEEN TEMPERS.

### TYPICAL HEAT TREAT RESPONSE

TEMPERING TEMP		HARDENING	
°F	°C	1750°F	955°C
As QUENCHED		59 HRC	
400	205	57 HRC	
500	260	55 HRC	
600	315	54 HRC	
700	371	53 HRC	
800	427	53 HRC	
900	480	52 HRC	
1000	538	51 HRC	
1100	552	47 HRC	